



The Use of Pit and Fissure Sealants

Robert J. Feigal, DDS, PhD¹ Kevin J. Donly, DDS, MS²

Abstract

This paper reviews key issues of sealant use and methodology and poses recommendations to inform the discussion toward a consensus statement by participants. A comprehensive review of sealant literature, including policy recommendations from previous conferences that reviewed best practices for sealant use, was completed. Building on previous review papers and on previous policy statements by dental and public health groups, this paper discusses key questions about sealant use in light of contemporary caries data and cost-benefit analyses. In addition, newest material advancements are reviewed to establish the next step in sealant improvement for young patients. (*Pediatr Dent* 2006;28:143-150)

KEYWORDS: FISSURE SEALANTS, PREVENTIVE DENTISTRY, PEDIATRIC DENTISTRY

The important topic of sealants was discussed during the American Academy of Pediatric Dentistry Pediatric Restorative Dentistry Consensus Conference held in San Antonio, Texas and subsequently published in *Pediatric Dentistry* (2002). Simonsen provided a literature review which is the most thorough and current published update on sealants.¹ Feigal, utilizing published data, prepared an evidence-based position paper with recommendations for sealant use in children and adolescents.² These recommendations were supported by all members of the consensus conference panel.

Since sealants play such a critical role in preventive dentistry, this topic was chosen to be a part of the AAPD Symposium on the Prevention of Oral Disease in Children and Adolescents (Chicago, November 11-12, 2005). Over the past three years, there have not been great changes in sealants or their recommended use, therefore an update of the previous paper seemed appropriate. The only significant change in these updated recommendations is associated with glass ionomer sealants, which may be considered appropriate for use in partially erupted teeth.

The dental battle against decay in pits and fissures has a long and creative past that includes such preventive innovations as early physical blocking of fissures with zinc phosphate cement,³ mechanical fissure eradication,⁴ prophylactic odontotomy,⁵ and chemical treatment with silver nitrate.⁶ Creativity in this effort against fissure caries

continues, with new materials and technologies tested each year. At the time that acid etch bonding to enamel was first described by Buonocore in 1955,⁷ bonding was a new technology, and a logical step in its use was the prevention of pit and fissure decay. Thus, resin sealants were born.⁸

New methods of caries prevention focus on pit and fissure caries because tooth surfaces with pits and fissures have always been the earliest and most prevalent of carious areas. The disproportion of caries on fissured surfaces continues to this day, with these surfaces accounting for over 80% of all caries in young permanent teeth.⁹

During the time of the first clinical sealant trials, caries rates were high. The strong probability of fissure caries on nearly all molars drove the profession to see sealants as a highly advantageous procedure. It was generally accepted that nearly all molar occlusal surfaces would eventually become carious.^{5,10-12} As reviewed by Eklund and Ismail,¹³ during the 1950s, 1960s and 1970s, 70% of all molar occlusal surfaces became carious within 10 years of emergence into the oral cavity. A high percentage of these occlusal lesions occurred in the first 3 years after eruption.^{12,14} These early caries data supported Council of Dental Research policy that sealants should be universally applied, principally to molar teeth within 3 or 4 years of eruption.¹⁵

More recent analyses indicate that caries susceptibility of molar occlusal surfaces is lower and more continuous, resulting in lower overall occlusal caries prevalence and an extended time of risk reaching into adulthood.^{13,16-18}

Caries rates have changed dramatically since the 1970s, with fewer of our present patients falling into high caries risk groups. While the caries attack has decreased in numbers, intensity, and speed on smooth surfaces, it also has decreased on occlusal surfaces. The concurrent reduction in fissure caries risk can be seen in analyses of NHANES

¹Dr. Feigal is professor and postdoctoral program director, Department of Preventive Sciences, School of Dentistry, University of Minnesota, Minneapolis, Minn; ²Dr. Donly is professor and chair, Department of Pediatric Dentistry, School of Dentistry, University of Texas Health Science Center at San Antonio, Texas.
Correspond with Dr. Donly at donly@uthscsa.edu

III data from the early 1990s.⁹ It is clear that there has been a dramatic change in occlusal surface caries over the US population of young patients, with pits and fissures accounting for 88% of caries in children while making up only 13% of total tooth surfaces. Therefore, the economic and health benefit for sealant treatment has undergone a redefinition based on the newer caries risk figures.¹⁸ A more contemporary perspective is that sealants should be directed to those teeth judged at risk for caries, not directed to all teeth with pits or fissures.

Questions concerning sealant use deserve reexamination:

1. Do contemporary changes in caries rates affect sealant use?
2. Should sealants be placed only on caries-free pits and fissures or can we seal over enamel caries?
3. Should sealants be placed on all noncarious pits and fissures?
4. Should sealant application be limited to the first years after eruption/emergence?
5. Can sealants be placed effectively on buccal and lingual pits and fissures?
6. Are sealants effective on primary teeth?
7. Can sealants be placed effectively immediately after a fluoride treatment?
8. What advances in dental materials have improved sealant effectiveness?

The purpose of this paper is to review previous large-group agreements on sealant use in light of the most contemporary literature. In the process, a goal is to uncover persistent beliefs and myths about sealants that need changing based on the newest research.

Previous dental organization guidelines on sealant use

Excellent reviews of sealant studies and thoughtful discussions of sealant philosophy exist.¹⁹⁻²³ These previous works were key to the evolution of the profession's present philosophy on sealants. They are required reading for anyone charged with making recommendations for sealant use. Nonetheless, these past conferences are products of their times, and they reflect the knowledge and the biases of the years in which they were held. Therefore, the previous work is a treasure of information for us today, but the conclusions drawn in each of these conferences are not fully relevant to the present situation. On the other hand, it is interesting to note how many of the ideas considered new and contemporary today were described at previous meetings. Most surprising is that some of the previous discussions included statements against myths that persist to this day, and most disappointing is that the collective wisdom of the profession has yet to take up many of the changes in thought and action strongly suggested in these past discussions.

The review chaired by Siegel²² stated that "sealants are an important dental caries prevention technology, ideally used in combination with patient education, effective

personal oral hygiene, fluorides and regular dental visits." In addition, this conference discussed determinants of sealant delivery in community programs and individual care programs. Among other recommendations were these key positions:

1. Caries risk assessment of the individual and the tooth are important as determinants of sealant need.
2. Caries risk on surfaces with pits and fissures may continue into adulthood; therefore, posteruptive age alone should no longer be used as a major criterion for sealant decisions.
3. Sealants should be used to prevent caries in at-risk teeth (preventive sealants).
4. Sealants should be used to treat teeth with questionable caries or definite caries confined to the enamel pits and fissures (therapeutic sealants).
5. Sealed teeth need to be evaluated periodically for sealant integrity and retention.

Sealant use in the context of contemporary caries epidemiology

Caries rates have fallen dramatically for populations in industrialized nations. Reasons for such a decrease have been previously described. The latest data analyses of caries²⁴⁻²⁶ illuminate subtleties in the changes in caries rates not previously appreciated. Population subgroups continue to experience the bulk of dental caries. Educational levels and socioeconomic status relate inversely with caries experience. Primary tooth caries rates and distributions differ from rates and distributions in permanent teeth.

For the purposes of this discussion, it is prudent to focus on changes in caries rates and distributions seen on tooth surfaces that suffer from pit and fissure caries. The surfaces most at risk for caries in young patients are occlusal surfaces of permanent first and second molars. The next most susceptible are buccal surfaces of lower molars and lingual surfaces of upper molars. Caries rates on all permanent tooth surfaces have dropped for each age level for 4 subsequent national caries surveys covering the years between 1971 and 1994.²⁷ While overall caries has decreased, surface specific caries rates illustrate important issues. As the overall smooth surface caries rate has decreased significantly, the percentage of total caries attributable to pits and fissures has increased. The latest evaluations suggest that pits and fissures account for about 80% of all caries in young US patients.⁹

A casual observer might conclude that there has been no decrease in occlusal surface caries, or that occlusal surface caries rates have increased. In fact, occlusal caries has also decreased dramatically. Initiation of new carious lesions in pits and fissures of molars 4 years after eruption has decreased more than 70% over 20 years and progression of lesions in the majority of the population has slowed. For example, prevalence of decayed or filled occlusal surfaces on permanent first molars in 10-year-old children dropped from about 55% to about 15% between national surveys in 1971-1974 and 1988-1994. In the same time period,

prevalence of decayed or filled occlusal surfaces on permanent second molars in 16-year-old children dropped from about 68% to about 25% (Figure).

Benefit analysis of sealants involves comparing caries rates on sealed teeth and caries rates on those surfaces that were not sealed. The decline in occlusal caries, therefore, affects benefit analyses. As the actual caries rate on nonsealed surfaces decreases, the number of sealants placed to “save” or protect one surface from caries must increase, and the computed percent effectiveness of the sealants decreases. For example, if 70 out of 100 nonsealed surfaces became carious in a study, while only 10 out of 100 sealed teeth became carious, the effectiveness would be 60 saved surfaces divided by 70 expected carious surfaces ($60/70=86\%$). If only 20 of those same unsealed teeth became carious in the study while 10 of the sealed teeth became carious, the effectiveness would be 10 saved surfaces divided by the 20 expected carious surfaces ($10/20=50\%$). The same caries rate on the sealed surfaces as shown in the 2 sides of this example is, therefore, viewed as much more effective when the comparison, or control, group develops caries at a higher rate.

From the previous example, it is clear that to gain the greatest benefit for the sealant treatment, it is imperative to determine caries risk of teeth and then to seal those that have the highest risk of caries. This understanding of risk-based sealant treatment is not new, but its adoption has been slow.

This concept of risk-based sealant application is supported by published data. A 5-year study of caries rates after sealant application on molars diagnosed into 2 groups, sound and incipient occlusal lesions, showed a dramatic difference in effectiveness of sealant placement.²⁸ In this study in a fluoridated community, molars scored initially as sound became carious at a rate of 13% if not sealed and a rate of 8% if sealed, representing a modest protective effect (13% vs 8%). Molars scored initially as incipient or questionable became carious at a rate of 52% if not sealed and a rate of 11% if sealed. This represents a striking protective effect (52% vs 11%).

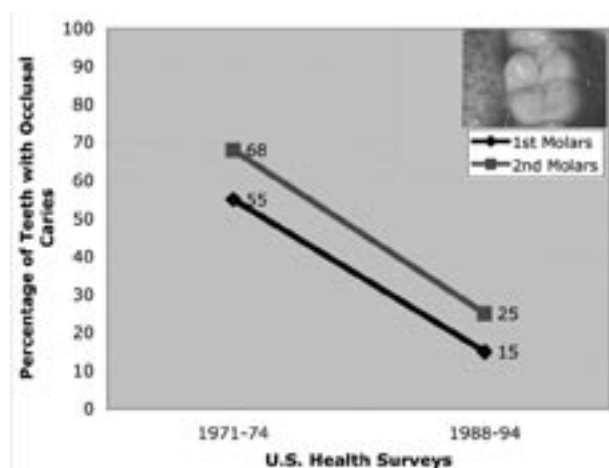


Figure 1. Changes in occlusal caries rates 4 years after eruption.

In another report, focused on a high-risk population, it was noted that permanent first molars with sealants received less subsequent restorative treatment than molars without sealants.²⁹

Information obtained by Anderson from the Delta Dental Data Analysis Center revealed that over a 4-year span, 239,443 children ages 7 to 15 years that were continually enrolled for dental benefits experienced 85% fewer carious lesions on all tooth surfaces when molar surfaces were sealed compared to 272,872 children of the same age that did not have sealants.³⁰

Along with changes in our contemporary understanding of the caries process on surfaces affected by pits and fissures has come the necessity to rethink sealant use. The majority of fissures and pits no longer are destined to become carious in the first 3 years after tooth eruption, and a significant number of fissures and pits will not become carious at all. The rate of caries initiation is slower and over a much longer span of time. Therefore, it is faulty to emphasize sealant placement only within a few years of eruption. Sealant use must be based on personal, tooth, and surface risk, and this risk may change at any time in the life of the patient. Many fissures are at risk immediately at eruption. Others are not, and therefore, should not be sealed. Alternatively, the unsealed and unrestored fissures may reach an at-risk stage later due to changes in a patient's habits, oral microflora or physical condition. Therefore, these fissures must continually be evaluated into adulthood, and sealants may be appropriate later in life.

Sealing enamel caries

Many reports have described arrested caries and the elimination of viable microorganisms under sealants or restorations with sealed margins.³¹⁻³³ Dentists are reluctant to accept these concepts even though investigations have clearly indicated the facts for 30 years. With the bulk of evidence increasing and a more open discussion about minimal intervention therapies for caries, ideas are changing. Professional leadership has advocated that any fissure lesion judged to be limited to enamel is a candidate for sealant therapy.²² This stance is supported by the large body of literature showing that lesions effectively sealed do not progress.

This position in favor of sealing early carious lesions should not be surprising. In retrospect, early caries has been watched or sealed over for decades. When we view the low sensitivity and specificity of current fissure diagnostic methods, it is clear that we have always misdiagnosed a significant number of fissures, calling between 20% to 80% of true enamel caries sound and diagnosing as carious about 5% to 20% of actually sound fissures.^{34,35} Depending upon the caries risk level of the population one is treating, a judgment must be made as to the relative value of general overdiagnosis or underdiagnosis. For most contemporary clinicians in fluoride-rich areas, it would be better to underdiagnose early caries, since many incipient lesions either become inactive, remineralize, or progress very slowly to cavitation and dentin involvement. Rather than surgical

intervention on all questionable or incipient fissure lesions, a more rational approach is to observe carefully until a time at which diagnosis is more clear, or to seal the questionable fissure to limit any future progression of the lesion.

Enameloplasty, caries-detecting dyes, and proper treatment codes

A logical extension of the treatment philosophy in favor of sealing early enamel lesions is an argument against enameloplasty of all fissures before sealant placement. Careful cleaning of the enamel surface and the fissure followed by effective etching of the fissure walls will result in a successful sealant and will halt progression of any existing incipient caries. Therefore, universal use of fissure eradication or enameloplasty with rotary instruments or air abrasion is an unnecessary addition to good sealant methodology. In addition, the enameloplasty procedure itself may injure normal enamel resulting in higher caries susceptibility of that fissure in the future.

While a large body of laboratory studies show potential benefits to enameloplasty, only a small number of short-term clinical studies with small samples support this technique as equal to, but not better than, sealant placement without enameloplasty.^{36,37} Most important to the decision on the use of enameloplasty methods is the fact that there are no long-term clinical studies to show that enameloplasty is safe. One could speculate that removal of enamel in areas of thin or no enamel (ie, the depth of fissures), leaves the tooth more susceptible to caries attack in the event of sealant loss. This has not been tested.

A recent in vitro study compared preparation of fissures vs no preparation and compared minimal sealant placement vs overfilling with sealant on teeth that were then thermally and mechanically stressed. The marginal leakage that occurred was greater in nonprepared fissures, suggesting that fissure preparation could improve sealants. Yet, greater than the benefit of fissure preparation was the improvement shown by minimal application of sealant as opposed to overfilling the occlusal surface leading to heavy occlusion on the tested sealant. One could suggest from these data that careful placement of the proper sealant volume is more beneficial than enameloplasty.³⁸

Despite the lack of long-term clinical evidence of benefit through enameloplasty prior to sealant placement, a majority of pediatric dentists use the technique, with 17% of respondents to a recent survey stating that they always used enameloplasty and 70% stating that they sometimes used enameloplasty.³⁹

Another extension of the logic of sealing early caries argues against the use of caries-detecting dyes in fissure caries diagnosis. The last remnants of caries in a fissure should be inconsequential to the success of the sealant. Surface cleaning is all that is appropriate, unless one judges a fissure to contain caries that has progressed to the dentin.

In addition, those who use fissure eradication procedures and/or caries-detecting solutions to justify placement of,

and charging for, a posterior composite rather than sealant often are overtreating the disease. They are working counter to policy of the ADA Council on Dental Benefit Programs. The Council policy since 2000 states that a sealant (CDT-code #D1351) is a “mechanically and/or chemically prepared enamel surface sealed to prevent decay” while a 1-surface posterior resin (CDT-code #2385) is “used to restore a carious lesion into the dentin...not a preventive procedure.”

Risk analyses and sealant use

It is appropriate to ask how to analyze the risk of caries in the process of decision-making for sealants. The topic is too large for this paper, but a summary is in order. As a deeper understanding of cariology develops, more insight is gained into the factors that predict caries. Therefore, the future will bring improvement to caries risk analyses. Presently, clinical studies indicate that an experienced dentist can make such a decision without expensive technology.⁴⁰ The best predictors are prior caries experience of the patient, fluoride history of the patient, fissure anatomy, and plaque load.^{41,42}

The main goal of a recommendation for risk-based decision-making for sealants is to have dentists actually make a decision, rather than to assume sealant application for every tooth. The formal process of the risk analyses may not be as important as the fact that some risk analysis is done followed by a decision to treat based on the risk analysis.

The need for vigilant recall and repair

A previous review of sealant clinical trials show a failure rate (judged by sealants needing repair, replacement or restoration) to be between 5% and 10% each year.⁴³ This number is supported in many large sealant studies and in numbers from private pediatric practices using the best of sealant procedures. Without appropriate clinical follow-up of these sealants, the failures would compound over a few years, leaving most of the surfaces equally susceptible to caries as surfaces that were never sealed. Long-term success of sealant therapy, therefore, is dependent upon vigilant recall and repair when necessary. With such follow-up, sealant success is very high. Studies that incorporated routine recall and maintenance report 80% to 90% success after a decade or more.^{44,45} To achieve long-term success through routine recall and maintenance appointments, children should have a dental home where oral health care maintenance can be appropriately provided.

The necessity of recall and maintenance for sealants is based on an understanding that partial loss of sealant leads to a surface at a risk for caries similar to one never sealed.^{46,47} One-time sealant placement does not impart any long-term caries protection unless the sealant remains in place and intact. Loss of coverage of any susceptible pit or fissure leads to an immediate risk of caries attack for the uncovered area. Newer data supporting this concept⁴⁸ report on treatment for permanent first and second molars over time with data derived from billing records in a large population of subjects covered by insurance and actively seeking care. Sealed molars showed a caries-reducing treatment effect at

3 years (6% on first molars and 9% on second molars), but this treatment effect did not increase significantly between 3 and 5 years after sealant placement. In other words, restorations did occur on sealed teeth at about the same rate as on nonsealed teeth after 3 years.

Sealants on primary teeth and on permanent teeth other than molars

The focus of most sealant studies is the occlusal surface of permanent teeth. Permanent molars have been selected as teeth most at risk for occlusal caries and thus, the teeth that most benefit from sealants. This perspective comes from population data. It reflects the realities of "normal" tooth anatomy and thus average susceptibility to caries. It does not account for individual differences among patients and among teeth. Such differences are the basis for risk analysis and decision-making in sealant care that is now recognized as necessary for the best cost-benefit ratio in sealant therapy.

Therefore, many primary teeth may be judged to be at risk due to fissure anatomy and/or patient caries risk factors. This also is true for permanent teeth other than molars (eg, incisors with deep lingual pits or premolars with incipient caries in deep occlusal grooves). Any teeth judged to be at risk can certainly benefit from sealant application.

Early suggestions that primary tooth enamel does not etch well and therefore was difficult to bond have been erased by successful acid etching of primary enamel. Much of our contemporary restorative treatment relies on this method of bonding and retention, and it has been successful in primary teeth. Clinical studies reporting on sealant success on primary molars are rare. Those that have been published report retention and success equivalent to permanent molar sealants.⁴⁹⁻⁵² Of course, patient behavior and compliance (and thus critical isolation and careful technique) are significant factors in sealant retention studies.⁵³

Not all clinicians and investigators are skilled with young patients, leading to a bias about the success of sealants on children. We must advocate for the acceptance of sealant placement on any tooth, primary or permanent, that is judged to be at risk for pit and fissure caries. The challenge, then, for any clinician is to provide the service in the most appropriate way, working with the patient to assure patient compliance and careful application of sealants.

Inclusion of primary molars, and any other teeth judged to be at risk for caries or having incipient lesions, as appropriate for sealant therapy should be a prominent recommendation.

Sealant placement immediately after fluoride treatment

For years there existed an opinion that a recent fluoride exposure, such as in-office fluoride treatment, would interfere with the etching pattern and, therefore, the retention of sealants. This opinion has been dispelled in several reports using sealant bonding and orthodontic bracket bonding.^{54,55} Therefore, sealant application can follow fluoride treatment during the same office appointment if desired.

Can sealants be placed effectively on buccal and lingual surface pits and fissures?

Few clinical sealant trials have measured effectiveness on buccal surfaces of mandibular molars and lingual surfaces of maxillary molars. Those few that have generally report greater failures on these surfaces than on occlusal surfaces.⁵⁶⁻⁵⁹ More recent work suggests that sealants can be placed successfully on buccal and lingual surfaces.⁵³ Of particular interest is the observation that adding an intermediate layer of bonding agent primer and adhesive is more advantageous on these surfaces than on occlusal surfaces.⁵³ This may be due to the added flexibility and stress-breaking effect afforded by the unfilled adhesive layer and the subsequent benefit of this flexibility on the sealant bond to buccal or lingual surfaces undergoing continuous flexion during mastication.

Sealant improvement through dental material advancements and technique changes

Several advancements in dental materials have potential benefit for sealant success. Many are new enough that little clinical data are available. Others have proven benefits.

An example of the former is the benefit of fluoride-containing sealants. While we intuit an advantage of placing sealants containing fluoride, no clinical studies exist to suggest a benefit of this fluoride content. Original inclusion of fluoride into bis-GMA or resin sealants resulted in very low levels of fluoride availability and release⁶⁰ compared to other dental materials such as glass ionomers. The latest methods of adding fluoride to resins may make it more available since the fluoride is less bound in the resin chemistry. However, proof of the clinical benefit has yet to be shown. Since the addition of fluoride to sealants has no detrimental effect on sealant retention,⁶¹ it is certainly appropriate to use fluoride-containing sealants, but an anticaries advantage from the fluoride has not been demonstrated.

A technique change with good data support is the inclusion of a bonding primer and adhesive layer between etched enamel and the sealant. This technique, first used in a successful attempt to minimize negative effects of salivary contamination of etched surfaces, has been shown effective in improving bond strength and minimizing microleakage in lab studies⁶²⁻⁶⁶ and a clinical study of sealants⁶⁷ when used on contaminated enamel. Further work on bonding to non-contaminated surfaces⁵³ has reported that use of single-bottle bonding systems as a layer between enamel and sealant in a clinical study decreased risk of failure of occlusal sealants 47% and reduced the risk of failure of buccal/lingual sealants by 65%.

It has been speculated that the benefit of this primer and adhesive layer under the sealant is based on a combination of moisture-chasing effects of the hydrophilic primers, increased flow imparted by the less viscous primer and adhesive, and increased flexibility of the combined polymerized primer/adhesive/resin complex. Together, these factors lead to a better initial bond and a more resilient long-term bond.

Even more recent advances in bonding chemistry may portend additional benefits to sealants for young patients. Self-etching primer and adhesive combinations may lead to a dramatic simplification of the steps involved in sealant application with equivalent sealant retention. Such simplification minimizes time of treatment, decreases the need for patient compliance, and minimizes potential errors in technique. Two-year data⁶⁸ show equivalent sealant retention on occlusal and buccal/lingual surfaces of permanent molars using the self-etching primer/adhesive Prompt L-Pop (3M ESPE, St. Paul, Minn) as compared to normal etch and seal methods on contralateral teeth. Eliminating the rinsing and drying steps from the normal method allow a 50% savings of time and a much greater comfort level for the patients. Self-etching adhesives require additional study, but the potential is great that improved chemistry will add to the success numbers for sealants in the near future.

Glass ionomer cements, due to brittleness and susceptibility to fracture under the occlusal forces developed during mastication, were traditionally not recommended for use as sealants. However, there are instances where glass ionomer sealants could be considered appropriate as an interim preventive material for occlusal surfaces before molars were completely erupted. Current literature has demonstrated the effectiveness of glass ionomer as a surface protectant. Some glass ionomers can flow into pits and fissures well and have been shown to be effective sealants over a 3.6-year evaluation period.⁶⁹⁻⁷²

Improvements in sealant materials may dramatically change the cost-benefit calculations. With more sealants staying in place, effectiveness improves. In addition, clinician judgment about where and when to use sealants may be altered, so that, ultimately, those surfaces most susceptible to decay could have the benefit of early sealant placement.

Recommendations

The dental literature supports:

1. Bonded resin sealants placed by appropriately trained dental personnel are safe, effective, and underused in preventing pit and fissure caries on at-risk surfaces. Effectiveness is increased with good technique, appropriate follow-up, and resealing as necessary.
2. Sealant benefit is increased by placement on surfaces judged to be at high risk or surfaces exhibiting incipient carious lesions. Placing sealant over minimal enamel caries has been shown to be effective at inhibiting lesion progression. Appropriate follow-up care, as with all dental treatment, is recommended.
3. Presently, the best evaluation of risk is done by an experienced clinician using indicators of tooth morphology, clinical diagnostics, caries history, fluoride history, and present oral hygiene.
4. Caries risk, and therefore potential sealant benefit, may exist at any age, in any tooth with a pit or fissure, including primary and permanent teeth in children and adults.

5. Sealant placement methods should include careful cleaning of the pits and fissures without removal of any appreciable enamel. Some circumstances may indicate use of a minimal enameloplasty technique.
6. A low-viscosity, hydrophilic bonding layer as part of, or under, the actual sealant has been shown to enhance the long-term retention and effectiveness.
7. Glass ionomer materials can be used as transitional sealants, and may prove to be effective as longer-term pit and fissure sealants.
8. The profession must be alert to new preventive methods effective against pit and fissure caries, including changes in dental materials or technology.

References

1. Simonsen RJ. Pit and fissure: review of the literature. *Pediatr Dent* 2002;24:398-414.
2. Feigal RJ. The use of pit and fissure sealants. *Pediatr Dent* 2002;24: 415-422.
3. Wilson IP. Preventive dentistry. *Dent Digest* 1895; 1:70-72.
4. Bodecker CF. Eradication of enamel fissures. *Dent Items* 1929;51:859-866.
5. Hyatt T. Prophylactic odontotomy: The cutting into the tooth for the prevention of disease. *Dent Cosmos* 1923;65:234-241.
6. Kline H, Knutson JW. Studies on dental caries XIII. Effect of ammoniacal silver nitrate on caries in the first permanent molar. *J Am Dent Assoc* 1942;29:1420-1426.
7. Buonocore MG. A simple method of increasing the adhesion of acrylic filling materials to enamel surfaces. *J Dent Res* 1955;34:849-853.
8. Cueto EI, Buonocore MG. Adhesives and caries prevention: a preliminary report. *Br Dent J* 1965; 119:77-80.
9. Brown LJ, Kaste L, Selwitz R, Furman L. Dental caries and sealant usage in U.S. children, 1988-1991: selected findings from the Third National Health and Nutrition Examination Survey. *J Am Dent Assoc* 1996;127:335-343.
10. Knutson JW, Klein H, Palmer CE. Studies on dental caries. VIII. Relative incidence of caries in the different permanent teeth. *J Am Dent Assoc* 1938; 25:1923-1934.
11. Klein H, Palmer CE. Studies on dental caries. XII. Comparison of the caries susceptibility of the various morphological types of permanent teeth. *J Dent Res* 1941;20:203-216.
12. Carlos JP, Gittelsohn AM. Longitudinal studies of the natural history of caries—II: A life-table study of caries incidence in the permanent teeth. *Arch Oral Biol* 1965;10:739-751.
13. Eklund SA, Ismail AI. Time of development of occlusal and proximal lesions: Implications for fissure sealants. *J Publ Health Dent* 1986;46:114-121.

14. Reid DB, Grainger RM. Variations in the caries susceptibility of children's teeth. *Hum Biol* 1955; 27:1-11.
15. Council on Dental Research. Cost effectiveness of sealants in private practice and standards for use in prepaid dental care. *J Am Dent Assoc* 1985;110:103.
16. Bohannon HM. Caries distribution and the case for sealants. *J Publ Health Dent* 1983;43:200-204.
17. Ripa LW, Leske GS, Varm AO. Longitudinal study of the caries susceptibility of occlusal and proximal surfaces of first permanent molars. *J Publ Health Dent* 1988;48:8-13.
18. Brown LJ, Selwitz RH. The impact of recent changes in the epidemiology of dental caries on guidelines for the use of dental sealants. *J Publ Health Dent* 1995;55(special issue):274-291.
19. National Institutes of Health. Dental sealants in the prevention of tooth decay. Consensus development conference. *J Dent Educ* 1984;48 (suppl):126-131.
20. Ripa LW, Bohannon HM, Callanen VA, et al. Preventing pit and fissure caries: a guide to sealant use. Boston, MA: Division of Dental Health, Massachusetts Department of Public Health, 1986.
21. American Dental Association, Council on Dental Health and Health Planning and Council on Dental Materials, Instruments, and Equipment. Pit and fissure sealants. *J Am Dent Assoc* 1987; 114:671-672.
22. Siegal MD. Workshop on Guidelines for sealant use. *J Publ Health Dent* 1995;55(special issue):259-311.
23. Rozier RG. Reaction paper. The impact of recent changes in the epidemiology of dental caries on guidelines for the use of dental sealants: Epidemiologic perspectives. *J Publ Health Dent* 1995;55(special issue):292-301.
24. Brown LJ, Wall TP, Lazar Y. Trends in untreated caries in permanent teeth of children 6 to 18 years old. *J Am Dent Assoc* 1999;130: 1637-1644.
25. Brown LJ, Wall TP, Lazar V. Trends in total caries experience: permanent and primary teeth. *J Am Dent Assoc* 2000a;131:223-231.
26. Brown LJ, Wall TP, Lazar V. Trends in untreated caries in primary teeth of children 2 to 10 years old. *J Am Dent Assoc* 2000b;131:93-100.
27. Kaste LM, Selwitz RH, Oldakowski RJ, Brunelle JA, Winn DM, Brown LJ. Coronal caries in the primary and permanent dentition of children and adolescents 1-17 years of age: United States, 1988-1991 *J Dent Res* 1996;75(special issue):631-641.
28. Heller KE, Reed SG, Bruner FW, Eklund SA, Burt BA. Longitudinal evaluation of sealing molars with and without incipient dental caries in a public health program. *J Publ Health Dent* 1995;55:148-153.
29. Bhuridej P, Damiano PC, Kuthy RA, Flach SD, Kanellis MJ, Heller KE, Dawson DV. Natural history of treatment outcomes of permanent first molars. A study of sealant effectiveness. *J Am Dent Assoc* 2005;136:1265-1272.
30. Personal communication, Dr. Maxwell H. Anderson, Delta Dental Database, Washington State, 2005.
31. Handelsman SL, Buonocore MG, Heseck DJ. A preliminary report on the effect of fissure sealant on bacteria in dental caries. *J Prosthet Dent* 1972;27:390-392.
32. Going RE, Loesche WJ, Grainger PA, Syed SA. The viability of microorganisms in caries lesions five years after covering with a fissure sealant. *J Am Dent Assoc*. 1978;97:455-462.
33. Mertz-Fairhurst EJ, Adair SM, Sams DR, et al. Cariostatic and ultraconservative sealed restorations: Nine-year results among children and adults. *J Dent Child* 1995; 62:97-107.
34. Ekstrand KR, Ricketts DNJ, Kidd EAM, Qvist U, Schou S. Detection, diagnosing, monitoring, and logical treatment of occlusal caries in relation to lesion activity and severity: An in vitro examination with histological validation. *Caries Res* 1998; 32:247-254.
35. Lussi A. Validity of diagnostic and treatment decisions of fissure caries. *Caries Res* 1991;25:296-303.
36. Le Bell Y, Forsten L. Sealing of preventively enlarged fissures. *Acta Odontol Scand* 1980; 38:101-104.
37. Shapira J, Eidelman E. Six-year clinical evaluation of fissure sealants placed after mechanical preparation: a matched pair study. *Pediatr Dent* 1986;8:204-205.
38. Geiger SB, Gulayev S, Weiss EI. Improving fissure sealant quality: mechanical preparation and filling level. *J Dent* 2000; 28:407-412.
39. Primosch RE, Barr ES. Sealant use and placement techniques among pediatric dentists. *J Am Dent Assoc* 2001;132:1442-1451.
40. Graves R, Abernathy J, Disney J, et al. University of North Carolina caries risk assessment study III. Multiple factors in caries prevalence. *J Publ Health Dent* 1991;51:134-143.
41. Arrow P. Oral hygiene in the control of occlusal caries. *Community Dent Oral Epidemiol* 1998; 26:324-330.
42. Rethman J. Trends in preventive care: caries risk assessment and indications for sealants. *J Am Dent Assoc* 2000;131(suppl):8S-12S.
43. Feigal RJ. Sealant and preventive restorations: review of effectiveness and clinical changes for improvement. *Pediatr Dent* 1998;20:85-92.
44. Romcke RG, Lewis DW, Maze BD, Vickerson RA. Retention and maintenance of fissure sealants over 10 years. *J Can Dent Assoc* 1990;56:235-237.
45. Wendt LK, Koch G, Birkhed D. On the retention and effectiveness of fissure sealant in permanent molars after 15-20 years: a short study. *Community Dent Oral Epidemiol* 2001;29:302-307.
46. Chestnutt IG, Schafer F, Jacobson APM, Stephen KW. The prevalence and effectiveness of fissure sealants in Scottish adolescents. *Br Dent J* 1994;77:125-129.

47. Mertz-Fairhurst EJ, Fairhurst CW, Williams JE, Della Giustina VE, Brooks JD. A comparative study of two pit and fissure sealants: seven-year results in Augusta, Georgia. *J Am Dent Assoc* 1984;109:252-255.
48. Dennison JB, Straffon LH, Smith RC. Effectiveness of sealant treatment over five years in an insured population. *J Am Dent Assoc* 2000; 131:597-605.
49. Simonsen RJ. The clinical effectiveness of a colored pit and fissure sealant at 24 months. *Pediatr Dent* 1980;2:10-16.
50. Duggal MS, Tahmassebi JF, Toumba KJ, Mavromati C. The effect of different etching times on the retention of fissure sealants in second primary and first permanent molars. *Int J Paediatr Dent* 1997; 7:81-86.
51. Hotuman E, Rolling I, Poulsen S. Fissure sealants in a group of 3-4-year-old children. *Int J Paediatr Dent* 1998;8:159-160.
52. Vrbek V. Retention of a fluoride-containing sealant on primary and permanent teeth 3 years after placement. *Quintessence Int* 1999;30:825-828.
53. Feigal RJ, Musherurue P, Gillespie B, Levy-Polack M, Quelhas I, Hebling J. Improved sealant retention with bonding agents: A clinical study of two-bottle and single-bottle systems. *J Dent Res* 2000;79:1850-1856.
54. Brannstrom M, Nordenvall KJ, Malmgran O. The effect of various pretreatment methods on the enamel in bonding procedures. *Am J Orthod* 1955; 74:522-530.
55. Warren DP, Infante NB, Rice HG, Turner SD, Chan JT. Effect of topical fluoride on retention of pit and fissure sealants. *J Dent Hygiene*. 2001;75:21-24.
56. Barrie AM, Stephan KW, Kay EJ. Fissure sealant retention: a comparison of three sealant types under field conditions. *Community Dent Health* 1990; 7:273-277.
57. Cooney PV, Hardwick F. A fissure sealant pilot project in a third party insurance program in Manitoba. *J Can Dent Assoc* 1994;60:140-145.
58. Futatsuki M, Kubota K, Yeh YC, Park K, Moss SJ. Early loss of pit and fissure sealant: a clinical and SEM study. *J Clin Pediatr Dent* 1995;19:99-104.
59. Messer LB, Calache H, Morgan MV. The retention of pit and fissure sealants placed in primary school children by Dental Health Services, Victoria. *Austr Dent J* 1997;42:233-239.
60. Garcla-Godoy F, Abarzua I, De Goes MF, Chan DC. Fluoride release from fissure sealants. *J Clin Pediatr Dent* 1997;22:45-49.
61. Morphis TL, Toumba KJ, Lygidakis NA. Fluoride pit and fissure sealants: a review. *Int J Paediatr Dent* 2000;10:90-98.
62. Hitt JC, Feigal RJ. Use of a bonding agent to reduce sealant sensitivity to moisture contamination: An in vitro study. *Pediatr Dent* 1992;14:41-46.
63. Borem LM, Feigal RJ. Reducing microleakage of sealants under salivary contamination: Digital-image analysis evaluation. *Quintessence Int* 1994; 25:283-289.
64. Choi JW, Drummond JL, Dooley R, Punwani I, Soh JM. The efficacy of primer on sealant shear bond strength. *Pediatr Dent* 1997;19:286-288.
65. Fritz UB, Finger WJ, Stean H. Salivary contamination during bonding procedures with one-bottle adhesive systems. *Quintessence Int* 1998;29:567-572.
66. Hebling J, Feigal RJ. Reducing sealant microleakage on saliva-contaminated enamel by using one bottle dentin adhesives as an intermediate bonding layer. *Am J Dent* 2000;13:187-191.
67. Feigal RJ, Hitt JC, Splieth C. Sealant retention on salivary contaminated enamel: A two year clinical study. *J Am Dent Assoc* 1993;124:88-97.
68. Feigal RJ, Quelhas I. Clinical trial of a self-etching adhesive for sealant application: success at 24 months with Prompt L-Pop. *Am J Dent* 2003;16:249-251.
69. Covey DA, Johnson WW, Hopper LR. Penetration of various pit and fissure sealants into occlusal grooves. *J Dent Res* 2004; 83(A):Sequence #359(Abstract #3471).
70. Arrow P, Riordan PJ. Retention and caries preventive effects of a GIC and a resin-based fissure sealant. *Community Dent Oral Epidemiol* 1995; 23:282-285.
71. Karlzen-Reuterving G, van Dijken JWV. A three-year follow-up of glass ionomer cement and resin fissure sealants. *J Dent Child* 1995; 62:108-110.
72. Simonsen RJ. Glass ionomer as fissure sealant—a critical review. *J Pub Health Dent* 1996;56:146-149.

Copyright of Pediatric Dentistry is the property of American Society of Dentistry for Children and its content may not be copied or emailed to multiple sites or posted to a listserv without the copyright holder's express written permission. However, users may print, download, or email articles for individual use.